












PSR-4000 CC01SE (SM-SCR) *(UL Name: PSR-4000JV / CA-40JV)*

LIQUID PHOTOIMAGEABLE SOLDER MASK

-  **Screen Print and Spray Application**
-  **Aqueous Developing Solder Mask**
-  **RoHS Compliant**
-  **Halogen-Free**
-  **Compatible with Lead-Free Processing**
-  **Wide Processing Window**
-  **Excellent Resistance to ENIG & Immersion Tin**
-  **Resistant to Hot Storage**
-  **Conforms to ICP SM-840E Requirements**
-  **Compatible to LASER Marking**
-  **Semi-Matte finishes**

PROCESSING PARAMETERS FOR PSR-4000 CC01SE (SM-SCR)

PSR-4000 CC01SE (SM-SCR) COMPONENTS:

PSR-4000 CC01SE (SM-SCR) / CA-40 CC01SE		
Mixing Ratio	80 parts	20 parts
Color	Green	White
Mixed Properties		
Solids	81%	
Viscosity	185 – 225 ps	
Specific Gravity	1.99	

MIXING

PSR-4000 CC01SE (SM-SCR) is supplied in pre-measured containers with a mix ratio by weight of 80 parts **PSR-4000 CC01SE (SM-SCR)** and 20 parts, **CA-40 CC01SE**. For Screen Printing, mix both components together for 10 – 15 minutes.

PRE-CLEANING

Prior to solder mask application, the printed circuit board surface needs to be cleaned. Various cleaning methods include Pumice, Aluminum Oxide, Mechanical Brush, and Chemical Clean. For full body gold an alkaline cleaner is recommended. All of these methods will provide a clean surface for the application of **PSR-4000 CC01SE (SM-SCR)**. Hold time after cleaning the pcb should be kept to a minimum to reduce the oxidation of the copper surfaces.

SCREEN PRINTING

- Method: Single Sided and Double Sided Screening
- Screen Mesh: 29 – 43 threads/cm (74 – 110 tpi)
 - Screen Mesh Angle: 22.5° Bias
 - Screen Tension: 20 - 28 Newtons
 - Squeegee: 60 – 80 durometer
 - Squeegee Angle: 27 – 35°
 - Printing Mode: Flood / Print / Print
 - Flood Pressure: 20 – 30 psi
 - Printing Speed: 2.0 – 9.9 inches/sec
 - Printing Pressure: 70 – 100 psi

PROCESSING PARAMETERS FOR PSR-4000 CC01SE (SM-SCR)

SPRAY APPLICATION Start by setting the atomization pressure at 30 psi and spray a panel. Increase the spray atomization pressure until you have a smooth non-mottled surface. If you exceed 35 psi add additional solvent and reset the atomization pressure back to 30 psi and repeat process until you get a smooth sprayed surface. Adjust the Pot Pressure to get the desired solder mask thickness that meets your coverage requirements.

Method: HVLP sprayer

- Needle Set: 5 – 6 turns out
- Gun temperature: 90 - 100°C
- Atomization air temperature: 90 - 100°C
- Pot Pressure: 10-15 psi, adjust to get desired solder mask coverage
- Atomization Pressure: 30-35 psi, start at the low setting and increase until there is no mottling
- Conveyor speed: 2.5 – 3.0 ft./min; as slow as production allows

TACK DRY CYCLE The Tack Dry step is required to remove solvent from the solder mask film and produce a firm dry surface. The optimum dwell time and oven temperature will depend on oven type, oven loading, air circulation, exhaust rate, and ramp times. Excessive tack dry times and temperature will result in difficulty developing solder mask from through holes and a reduction in photo speed. Insufficient tack dry will result in artwork marking and/or sticking. Typical tack dry conditions for **PSR-4000 CC01SE (SM-SCR)** are as follows:

- Oven Type: Conventional Batch or Conveyor
- Oven Temperature: 66 - 80°C (150 - 176°F)
- For Single-Sided (Batch Oven)
 - 1st Side: Dwell Time: 15 - 20 minutes
 - 2nd Side: Dwell Time: 15 - 40 minutes
- For Double-Sided (Batch or Conveyor)
- Dwell Time: 30 - 60 minutes
- Oven Type: IR or IR assisted
 - Conveyor Speed: 2.7 – 3.2 ft./min
 - Time above 80°C: 2 – 2.1 minutes
 - Maximum Peak Temperature: 115°C
 - Total Dwell Time: 3 – 6 minutes

PROCESSING PARAMETERS FOR PSR-4000 CC01SE (SM-SCR)

EXPOSURE **PSR-4000 CC01SE (SM-SCR)** requires UV exposure to define solder mask dams and features. The spectral sensitivity of **PSR-4000 CC01SE (SM-SCR)** is in the area of 365 nm. Exposure times will vary by bulb type, age of the bulb and light source type. Below are guidelines for exposing **PSR-4000 CC01SE (SM-SCR)** using standard flood exposure equipment. Retention of smallest feature will determine the exposing energy.

- Exposure Unit: 8 kW or higher
- Stouffer Step 21: **Clear 8 minimum** (on metal / under phototool)
- Energy: 250 mJ / cm² minimum (under phototool)

DEVELOPMENT **PSR-4000 CC01SE (SM-SCR)** is developed in an aqueous sodium or potassium carbonate solution. Developing can be done in either a horizontal or vertical machine.

- Solution: 1% by wt. Sodium Carbonate or 1.2% Potassium Carbonate
- pH: 10.6 or greater
- Temperature: 85 - 95°F (29 - 35°C)
- Spray Pressure: 25 - 45 psi (1.7 – 3.1 bars)
- Dwell Time in developing chamber: 45 - 120 seconds
- Water rinse is needed to remove developer solution followed by a drying step

FINAL CURE **PSR-4000 CC01SE (SM-SCR)** requires a thermal cure to insure optimal final property performance. Thermal curing can be done in a batch oven or conveyorized oven.

- Temperature: 275 – 300°F (135 – 149°C)
- Time at Temperature: 45 – 60 minutes

UV CURE To improve moisture and chemical resistance a UV cure of 2 – 3 J/cm² is recommended.

For Process Optimization please contact your local Taiyo America Representative

FINAL PROPERTIES FOR PSR-4000 CC01SE (SM-SCR)

IPC-SM-840E, Class H & T, Solder Mask Vendor Testing Requirements

TEST	SM-840 PARAGRAPH	REQUIREMENT	RESULT
Visual	3.3.1	Uniform in Appearance	Pass
Curing	3.2.5.1	Ref: 3.6.1.1, 3.7.1 and 3.7.2	Pass
Non-Nutrient	3.2.6	Does not contribute to biological growth	Pass
Pencil Hardness	3.5.1	Minimum "F"	Pass – 6H
Adhesion	3.5.2.1	Rigid – Cu, Ni, FR-4	Pass
Adhesion	3.5.2.6	Doubled Layered Solder Mask	Pass
Machinability	3.5.3	No Cracking or Tearing	Pass
Resistance to Solvents and Cleaning Agents	3.6.1.1	Table 3 Solvents	Pass
Hydrolytic Stability and Aging	3.6.2	No Change after 28 days of 95-99°C and 90-98% RH	Pass
Solderability	3.7.1	No Adverse Effect J-STD-003	Pass
Resistance to Solder	3.7.2	No Solder Sticking	Pass
Resistance to Solder	3.7.3	No Solder Sticking	Pass
Simulation of Lead Free Reflow	3.7.3.1	No Solder Sticking	Pass
Dielectric Strength	3.8.1	500 VDC / mil Minimum	3123 VDC/mil (123 VDC / μm)
Thermal Shock	3.9.3	No Blistering, Cracking or De-lamination	Pass

Specific Class "H" Requirements

TEST	SM-840 PARAGRAPH	REQUIREMENT	RESULT
Flammability	3.6.3	UL 94V-0	Pass, File #E166421
Insulation Resistance	3.8.2		
Before Soldering		5×10^8 ohms minimum	Pass (2.0×10^{13} ohms)
After Soldering		5×10^8 ohms minimum	Pass (3.2×10^{13} ohms)
Moisture & Insulation Resistance	3.9.1		
Before Soldering–In Chamber		5×10^8 ohms minimum	Pass (3.2×10^{11} ohms)
Before Soldering–Out of Chamber		5×10^8 ohms minimum	Pass (2.8×10^{12} ohms)
After Soldering–In Chamber		5×10^8 ohms minimum	Pass (7.7×10^{10} ohms)
After Soldering–Out of Chamber		5×10^8 ohms minimum	Pass (7.6×10^{12} ohms)
Electrochemical Migration	3.9.2	$>2.0 \times 10^6$ ohms, no growth	Pass (1.3×10^{12} ohms)

TECHNICAL DATA SHEET



FINAL PROPERTIES FOR PSR-4000 CC01SE

Specific Class “T” Requirements

TEST	SM-840 PARAGRAPH	REQUIREMENT	RESULT
Flammability	3.6.3	Bellcore O ₂ Index – 28 minimum	Pass – 89
Insulation Resistance	3.8.2		
Before Soldering		5 x 10 ⁸ ohms minimum	Pass (1.5 x 10 ¹¹ ohms)
After Soldering		5 x 10 ⁸ ohms minimum	Pass (6.5 x 10 ¹⁰ ohms)

Specific Class “T” Requirements

TEST	SM-840 PARAGRAPH	REQUIREMENT	RESULT
Moisture & Insulation Resistance	3.9.1		
Before Soldering–In Chamber		5 x 10 ⁸ ohms minimum	Pass (1.6 x 10 ⁹ ohms)
Before Soldering–Out of Chamber		5 x 10 ⁸ ohms minimum	Pass (1.8 x 10 ¹³ ohms)
After Soldering–In Chamber		5 x 10 ⁸ ohms minimum	Pass (2.5 x 10 ⁹ ohms)
After Soldering–Out of Chamber		5 x 10 ⁸ ohms minimum	Pass (9.2 x 10 ¹² ohms)
Electrochemical Migration	3.9.2	< 1 decade drop, no dendritic growth	Pass

Additional Tests / Results

TEST	REQUIREMENT	RESULT
Surface Tension after Cure	Internal test; greater than 40 dynes/cm	42
CTI (Comparative Tracking Index)	ASTM-D-3638-07	≥600
Adhesion	GIP-008AA (TAIYO Internal Test Method) Cross-cut tape stripping test	100/100
Solder Heat Resistance	Solder float test: Rosin Flux 300°C/30sec., 1 cycle	Pass
Solvent Resistance	PGM-AC dipping, temp 20°C. / 20 min, Tape peeling test	Pass
Acid Resistance	10 vol% H ₂ SO ₄ , temp 20°C. / 20 min, Tape peeling test	Pass
Alkaline Resistance	10 wt% NaOH, temp 20°C. / 20 min, Tape peeling test	Pass
Electroless Ni/Au	TAIYO Internal Test Method Ni: 3 microns, Au: 0.03 microns	Pass
Immersion Tin Plating resistance	TAIYO internal test method Tin thickness: about 1 um	Pass
Hot Storage Resistance	160°C for 1000 hours – cross hatch adhesion (Mec Etch pretreatment)	Pass
Hot Storage Resistance	150°C for 2000 hours – cross hatch adhesion (Mechanical Brush pretreatment)	Pass

TECHNICAL DATA SHEET



FINAL PROPERTIES FOR PSR-4000 CC01SE

Additional Tests / Results

Legend Ink Adhesion	Tape test: <ul style="list-style-type: none"> LPI Legend – PSR-4100 WL(HD) Thermal Legend – S-200W UV Legend – UVR-110W Inkjet – IJR-4000 MW300 	Pass Pass Pass Pass
Gloss after Final Cure	Internal test; recorded at 60° angle <ul style="list-style-type: none"> PSR-4000 CC01SE Matte PSR-4000 CC01SE Semi-Matte 	<19 20 - 30
Conformal Coat Adhesion	Crosshatch adhesion/tape test: <ul style="list-style-type: none"> Dow Corning 1-2577 (Silicone) Humiseal 1B51 (Synthetic Rubber) Humiseal 1B73 (Acrylic) Humiseal 2A64 (Urethane) Cytec CE 1155 (Urethane) 	Pass Pass Pass Pass Pass
Halogen Level	Halogen Free if < 900 ppm	285 ppm
Outgassing Test ASTM E595 A 2 J/cm ² UV Cure was done after thermal cure	TML ≤ 1% CVCM ≤ 0.10%	TML-0.87% CVCM-<0.01%
Dk / Df	Internal Test at: 1.1 GHz 5.1 GHz 10.0 GHz 19.8 GHz	Dk / Df 3.6 / 0.022 3.6 / 0.021 3.5 / 0.021 3.5 / 0.020

Taiyo America, Inc. (TAIYO) warrants its products to be free from defects in materials and workmanship for the specified warranty period **PSR-4000 CC01SE (SM-SCR) / CA-40 CC01SE Warranty period is 12 Months** provided the customer has, at all times, stored the ink at a temperature of 68°F or less. TAIYO accepts no responsibility or liability for damages, whether direct, indirect, or consequential, resulting from failure in the performance of its products. If a TAIYO product is found to be defective in material or workmanship, its liability is limited to the purchase price of the product found to be defective. TAIYO MAKES NO OTHER WARRANTY, EXPRESS OR IMPLIED, AND MAKES NO WARRANTY OF MERCHANTABILITY OR OF FITNESS FOR ANY PARTICULAR PURPOSE. TAIYO'S obligation under this warranty shall not include any transportation charges or costs of installation or any liability for direct, indirect, or consequential damages or delay. If requested by TAIYO, products for which a warranty claim is made are to be returned transportation prepaid to TAIYO'S factory. Any improper use or any alteration of TAIYO'S product by the customer, as in TAIYO'S judgment affects the product materially and adversely, shall void this limited warranty.

FINAL PROPERTIES FOR PSR-4000 CC01SE

Hot Storage Photographs: 200°C for 250, 500, 1000 and 2000 hours – cross hatch adhesion (Mechanical Brush pretreatment). No cracking at the corners.

Photo 1: after 250 hours over copper



Photo 2: after 250 hours over FR4 laminate



Photo 3: after 500 hours over copper



Photo 4: after 500 hours over FR4 laminate



Photo 5: after 1000 hours over copper




Photo 6: after 1000 hours over FR4 laminate



Photo 7: after 2000 hours over copper



Photo 8: after 2000 hours over FR4 laminate

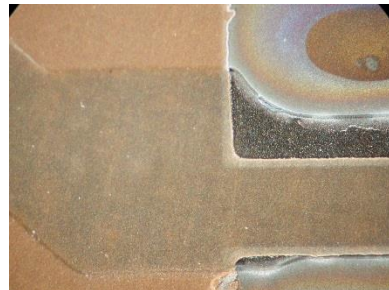

TECHNICAL DATA SHEET



FINAL PROPERTIES FOR PSR-4000 CC01SE

Legend Ink Adhesion: PSR-4000 CC01SE was coated with various types of Taiyo legend ink. Below are photos after tape testing of LPI, Thermal Cure, UV Cure and Inkjet.

Photo 9: LPI Legend, PSR-4100WL (HD)



Photo 10: Thermal Cure Legend, S-200W

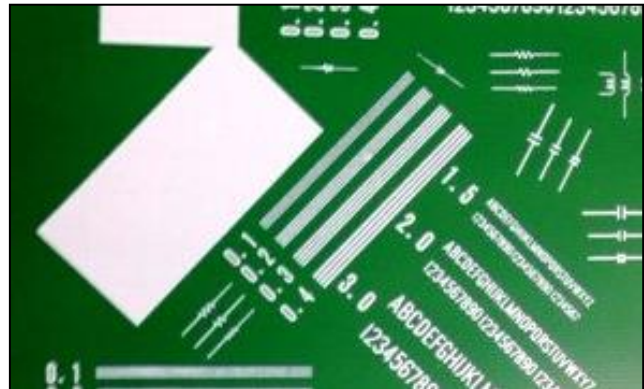


Photo 11: UV Cure Legend, UVR-110W



Photo 12: Inkjet Legend, IJR-4000 MW300

